

## Adsorption of Ni(II) Ion onto Calcined Eggshells: A Study of Equilibrium Adsorption Isotherm

Hans Kristianto, Novitri Daulay, and Arenst Andreas Arie\*

Department of Chemical Engineering, Faculty of Industrial Technology, Parahyangan Catholic University,  
Jl. Ciumbuleuit 94, Bandung 40141, Indonesia

\* **Corresponding author:**

email: arenst@unpar.ac.id

Received: October 20, 2017

Accepted: May 2, 2018

DOI: 10.22146/ijc.29200

**Abstract:** Adsorption is one of the most effective and economical method to treat heavy metals in water. In this study, we utilize waste chicken eggshells as biosorbent to adsorb Ni(II). Furthermore we study the effect of eggshell calcination on its adsorption performance. The effect of calcination on the characteristic of eggshell was observed using Fourier Transform Infrared Spectroscopy (FTIR) and Scanning Electron Microscope-Energy Dispersive X-ray Spectroscopy (SEM-EDS). It could be observed that  $\text{CaCO}_3$  in eggshell was converted into CaO, and from SEM images the calcined eggshell became more porous than the uncalcined one. The effect of various parameters such as initial Ni(II) solution pH and initial Ni(II) concentration was investigated using batch adsorption experiments. The data obtained then was fitted to Langmuir, Freundlich, Temkin, and Dubinin-Radushkevich isotherms. The best pH for Ni(II) adsorption was found to be 6. From Langmuir and Dubinin-Radushkevich isotherms, it was found that calcined eggshells gave 60 times higher maximum adsorption capacity than uncalcined one. This increase was possible due to more porous structure of calcined eggshells. The adsorption process was found to be exothermic and physisorption. This result was confirmed by the decrease of % removal with increase of temperature. Furthermore, Langmuir isotherm was found to be the best model, indicating adsorption of Ni(II) was monolayer adsorption on homogenous surface.

**Keywords:** adsorption; adsorption isotherm; eggshells; nickel ion

### ■ INTRODUCTION

Nickel is a silvery white metal that used in various industries, such as stainless steel, electroplating, battery, etc. However, the presence of nickel ion, Ni(II), in water could pose serious threat to human health and environment [1-2]. Ni (II) is known as toxicant for human, and its toxicity is depending on the exposure route. It is known as hemotoxic, immunotoxic, neurotoxic, genotoxic, reproductive toxic, hepatotoxic, and carcinogenic [3]. According to regulation of Indonesia State Ministry of Environment No 5 (2014), the maximum acceptable limit of Ni(II) discharged wastewater is 0.5 mg/L [4]. Thus, the wastewater must be treated before being discharged to comply the limit. Various technology has been used to treat Ni(II) in water, such as precipitation, ion exchange, membrane filtration,

coagulation-flocculation, and adsorption [5]. Among those technologies, adsorption using bio sorbent is known to be effective and economical method. One of potential bio sorbent is chicken eggshells.

Chicken egg is one of nutrition source, such as protein, folic acid, choline, vitamin A, B, D, E, and K [6] with high consumption in Indonesia and worldwide. In Indonesia, 1.43 million tones eggs were produced in 2016 [7], and predicted to increase in the future. This high production presents a problem because about 11%w of eggs is eggshells, which is inconsumable. Usually the eggshells are treated as waste, even though it possesses high potency for value-added products, such as nutritional supplement [8], fertilizer [6], catalyst [9], production of hydroxyapatite [10], and adsorbent [11]. Various heavy metals adsorption using eggshells has been done before, such as Cd(II) [12-13], Cr(III) [14],

Cr(VI) [15], Fe(III) [16], Al(III), Fe(II), Zn(II) [17], Cu(II) [18-19] and Pb(II) [11]. Study of comparison eggshell and calcined eggshell as adsorbent was done by Park et al. (2007) resulted on faster adsorption kinetics for Cd(II) and Cr compared to uncalcined one. Uncalcined [20-21] and calcined [22] eggshells has been used as Ni(II) adsorbent before. However, to the best of authors knowledge, the study of adsorption isotherm models has never been done before, especially for Ni(II) adsorption using uncalcined and calcined eggshells.

The aim of this study is to investigate the potential application of uncalcined and calcined eggshells for removal of Ni(II) from synthetic solution. Batch adsorption study was done to investigate the effect of initial solution's pH, initial Ni(II) concentration and temperature on Ni(II) adsorption. Langmuir, Freundlich, Temkin and Dubinin-Radushkevich adsorption isotherms were used to analyze the equilibrium data.

## ■ EXPERIMENTAL SECTION

### Preparation of Adsorbents

Chicken eggshells was collected from local market in Bandung, Indonesia. The eggshells was cleaned from the membranes, repeatedly washed to remove impurities using distilled water, and then oven dried at 110 °C for 24 h. Dried eggshells (ES) was crushed to powder to obtain particle size below 100 mesh. Calcination process was done at 850 °C for 4 h using electrical muffle furnace to obtained calcined eggshells powder (CES). Both of ES and CES were characterized using FTIR (Shimadzu FTIR, KBr pellet method) and SEM-EDS (FE-SEM, S4100. HITACHI) to observe the changes before and after calcination.

### Batch Equilibrium Study

The experiment was done using batch reactor equipped with stirrer (250 rpm), in which 500 mL of Ni(II) solution (NiSO<sub>4</sub>·6H<sub>2</sub>O from Merck, p.a) was placed. The initial pH of the Ni(II) solution was measured and adjusted using NaOH and HCl 0.1 M. Initial solution pH study was done at room temperature, and initial Ni(II) concentration of 10 mg/L, with pH variation at 2, 6, and

9. Adsorption temperature study was done at optimum pH, and initial Ni(II) concentration of 10 mg/L, while temperature was kept at room temperature (25 ± 1 °C). For confirmation of Temkin isotherm, adsorption was also done at 35 and 45 °C. The solution was heated using hotplate until the desired temperature was achieved. Adsorption isotherms study was done at optimum pH and room temperature, with variation of initial Ni(II) concentration (10, 20, 30, 50, and 60 mg/L). The amount of adsorbent used was 500 mg of ES and 10 mg of CES in this batch equilibrium study.

Five mL of sample solution was taken at initial and equilibrium to determine the concentration of Ni(II) in the solution. Before analysis, the sample was centrifuged at 6,000 rpm for 15 min. The adsorbed Ni(II) was calculated using Eq. (1), where  $q_e$  (mg/g adsorbent) was the mass of Ni(II) adsorbed per g of adsorbent,  $C_o$  and  $C_e$  (mg/L) were initial and equilibrium concentration of Ni(II) in the solution,  $V$  (L) was the volume of solution, and  $m$  (g) the mass of adsorbent used. The % removal was calculated using Eq. (2).

$$q_e = (C_o - C_e) \times \frac{V}{m} \quad (1)$$

$$\% \text{removal} = \frac{C_o - C_e}{C_o} \times 100\% \quad (2)$$

### Analysis of Ni(II)

The concentration of Ni(II) was analyzed using the color developing method with spectrophotometer UV/Vis measurement as described in [23] at a maximum wavelength of 470 nm. To summarize, 2 mL of sample aliquot was put in 50 mL measuring flask, then 1 mL H<sub>2</sub>SO<sub>4</sub> 1 M, 2 mL Na<sub>2</sub>C<sub>4</sub>H<sub>4</sub>O<sub>6</sub> 20%, 8 mL K<sub>2</sub>S<sub>2</sub>O<sub>8</sub> 5%, 0.5 mL alkaline dimethylglyoxime (DMG) 1%, and 2.5 mL NaOH 5 N were added and made up to 50 mL using distilled water. All reagents and chemicals used were obtained from Merck with pro analysis grade. These mixtures were allowed to stand for 30 min for color development prior to spectrophotometer measurement. The Ni(II) concentration in the sample was calculated from the calibration curve prepared with standard solutions of Ni(II).

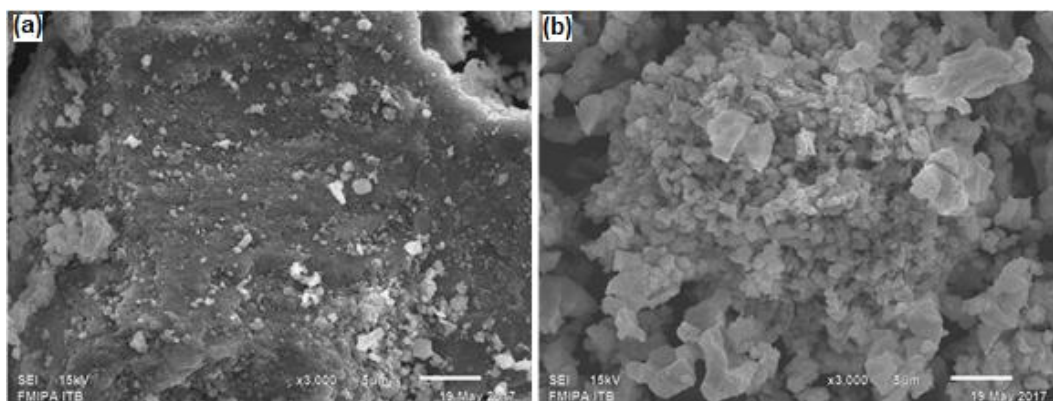


Fig 1. SEM images of ES (a) and CES (b) (magnification of 3,000×, scale bar 5 µm)

## ■ RESULTS AND DISCUSSION

### Characterization of ES and CES

The morphology of ES and CES is presented in Fig. 1. It could be observed that ES sample had irregular particle shape, with small pores on its surface. After calcination, the structure changed into agglomeration of rod-like structures with bigger pores. The more developed pore structure of CES could provide higher surface area than ES [24]. Similar results were also reported in previous studies [25-27].

The effect of calcination to functional groups of eggshell was studied by FTIR spectra, presented in Fig. 2. At ES sample, it could be observed peaks at 1798  $\text{cm}^{-1}$ , indicating carbonate C=O bond [28], 1425, 876, and 712  $\text{cm}^{-1}$  that indicate asymmetric stretch, out of plane bend, and in-plane bend vibration of carbonate [26,29-30]. While at CES sample, it could be observe that the carbonate peaks was decreasing, and new sharp peak at 3643  $\text{cm}^{-1}$  was formed. This peak indicates O-H stretching vibration of  $\text{Ca}(\text{OH})_2$  [28-29,31] that was formed after calcination. This result was confirmed by the SEM-EDS analysis, presented in Table 1. There was decrease of C's % mass before and after calcination process, indicating the decomposition of calcium carbonate. It is known that the eggshell was mainly composed of calcium carbonate [32], which released carbon dioxide gas during calcination, leaving CaO as the main product of the process (shown in reaction 1).

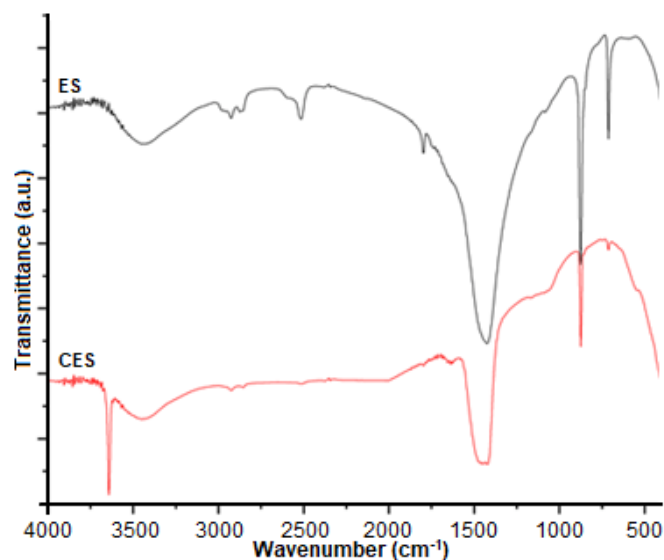


Fig 2. FTIR spectra of ES and CES


Table 1. The composition of eggshell before (ES) and after calcination (CES)

Element	% mass	
	ES	CES
C	21.32	7.23
O	53.00	53.65
Ca	25.67	36.12

### Adsorption Studies

#### Effect of initial pH

Langmuir isotherm follows assumption of monolayer adsorption with finite number of identical adsorption sites, homogenous adsorption, and no transmigration of adsorbate in the plane of adsorbent

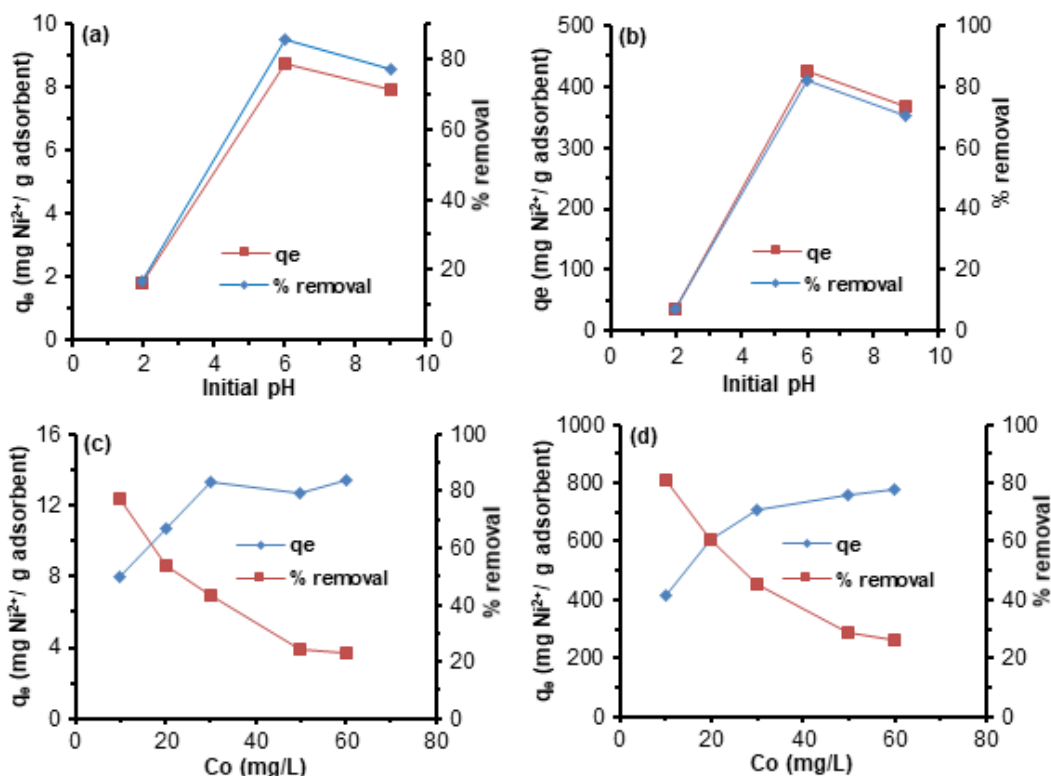

**Fig 3.** Effect of initial pH (a) ES, (b) CES and initial Ni(II) concentration (c) ES, (d) CES to  $q_e$  and % removal of Ni(II)

surface [36]. The equation is presented in Eq. (3), and its linearized form is shown in Eq. (4).

$$q_e = \frac{K_L q_m C_e}{1 + K_L C_e} \quad (3)$$

$$\frac{C_e}{q_e} = \frac{C_e}{q_m} + \frac{1}{K_L \cdot q_m} \quad (4)$$

From the result obtained, it could be observed that calcination of eggshell gave higher maximum adsorption capacity ( $q_m$ ), with increase of 60 times. The characteristic of Langmuir isotherm could be observed from non-dimensional parameter,  $R_L$ , which calculated using Eq. (5). The value of  $R_L$  indicates irreversible ( $R_L = 0$ ), linear ( $R_L = 1$ ), unfavorable ( $R_L > 1$ ), and favorable adsorption ( $0 < R_L < 1$ ) [37].

$$R_L = \frac{1}{1 + K_L C_0} \quad (5)$$

It could be observed that the adsorption process of Ni(II) onto ES and CES in this study is favorable, and with  $R^2$  value of 0.955 and 0.990 for ES and CES respectively, proving that the adsorption data was well fitted to Langmuir isotherm.

### Freundlich isotherm

Freundlich isotherm is usually used to describe adsorption at heterogeneous surface energies, with non-ideal, reversible and multilayer adsorption process. The equation is presented in Eq. (6), and its linearized form is shown in Eq. (7).


$$q_e = K_f \cdot C_e^{1/n} \quad (6)$$

$$\log q_e = \log K_f + \frac{1}{n} \log C_e \quad (7)$$

The  $K_f$  value indicates adsorption capacities [37], with increase of 52 times due to calcination process. The  $1/n$  value indicates favorability of adsorption process when  $0 < 1/n < 1$ , and cooperative adsorption when  $1/n > 1$  [36]. It could be observed that the adsorption of Ni(II) was favorable. The  $R^2$  value is lower for ES (0.8762) than CES (0.9578).

### Temkin isotherm

The Temkin isotherm incorporates interaction of adsorbate and adsorbent in adsorption process, also heat of adsorption (function of temperature) of molecules

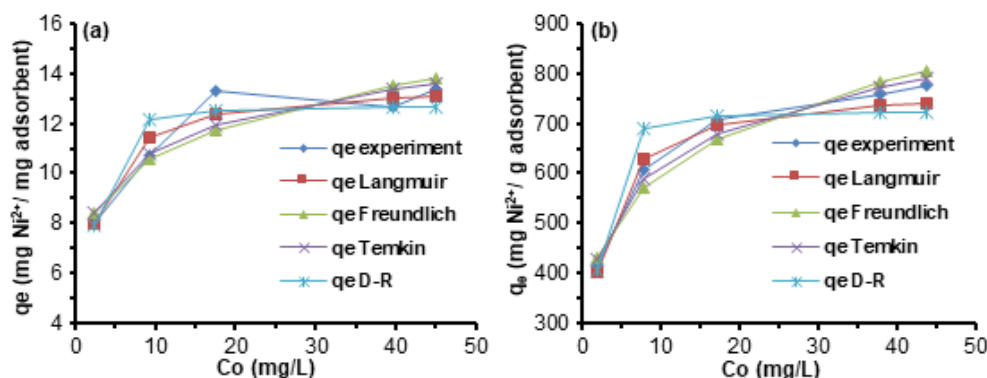

**Fig 4.** Plot of  $q_e$  vs  $C_e$  of experimental data and calculated  $q_e$  from various adsorption isotherm for (a) ES and (b) CES at initial solution pH 6 and room temperature

**Table 2.** Constants of adsorption isotherm

Isotherm	Constants	ES	CES
<b>Langmuir</b>	$q_m$ (mg Ni <sup>2+</sup> /g adsorbent)	13.531	769.23
	$K_L$ (L/mg Ni <sup>2+</sup> )	0.6017	0.5652
	$R_L$	0.0276 - 0.1379	0.0289 - 0.1477
	$R^2$	0.9553	0.9901
<b>Freundlich</b>	$K_F$ (L/mg)	7.258	378.22
	$1/n$	0.16807	0.20003
	$R^2$	0.8765	0.9578
<b>Temkin</b>	$\alpha$ (L/g adsorbent)	49.543	20.513
	$\beta$ (J/mol)	1.7607	116.04
	$R^2$	0.8712	0.9821
<b>Dubinin-Radushkevich</b>	$K$ (mol <sup>2</sup> /J <sup>2</sup> )	$6.14 \times 10^{-7}$	$5.48 \times 10^{-7}$
	$q_m$ (mg Ni <sup>2+</sup> /g adsorbent)	12.654	722.06
	$E$ (J/mol)	902	955
	$R^2$	0.8762	0.9112

decrease linearly to its assumption [36]. The linearized Temkin equation is presented in Eq. (8), where  $\alpha$  is equilibrium binding constant that represents the maximum binding energy, and  $\beta$  indicates the heat of adsorption [38]. Furthermore, the  $\beta$  could be defined as presented in Eq. (9), where  $R$  is universal gas constants,  $T$  is temperature (K), and  $\Delta Q = (-\Delta H)$  represents the adsorption energy [39].

$$q_e = \beta \ln \alpha + \beta \ln C_e \quad (8)$$

$$\beta = \frac{RT}{\Delta Q} \quad (9)$$

The positive  $\beta$  value indicates exothermic adsorption phenomenon [39-40] for both ES and CES. This result was then confirmed with a decrease of Ni(II)

removal and  $q_e$  with an increase of temperature, as shown in Fig. 5.

#### **Dubinin-Radushkevich isotherm**

The Dubinin-Radushkevich isotherm is usually used to observe the amount of adsorbed as function of adsorbate, which is assumed to be a Gaussian function of the Polanyi potential ( $\epsilon$ ) [36,41]. The linearized form and the Polanyi potential are presented in Eq. (10) and (11), respectively. This isotherm is usually used to differentiate physical and chemical adsorption of metal ions [36] by observing the mean free energy value ( $E$ ), which is calculated using Eq. (12). When the  $E$  value less than 8 kJ/mol, it indicates the adsorption process is physisorption, while  $E$  value between 8 to 16 kJ/mol



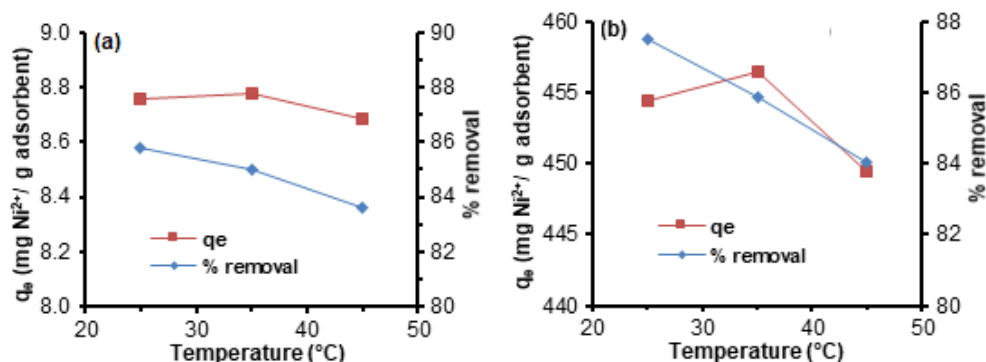


Fig 5. Effect of initial adsorption temperature (a) ES, (b) CES to  $q_e$  and % removal of Ni(II)

indicates adsorption process following ion-exchange, and the value of  $E$  in range of 20 to 40 kJ/mol indicates chemisorption [42]. The calculated  $E$  value from this study is below 8 kJ/mol, indicating the adsorption of Ni(II) onto ES and CES is following physisorption. The monolayer capacity of the adsorbent ( $q_m$ ) obtained from Dubinin-Radushkevich equation was also in a good agreement with  $q_m$  value obtained by Langmuir isotherm.

$$\ln q_e = \ln q_m - K \cdot \varepsilon^2 \quad (10)$$

$$\varepsilon = RT \ln \left( 1 + \frac{1}{C_e} \right)^2 \quad (11)$$

$$E = \frac{1}{\sqrt{2K}} \quad (12)$$

Based on the  $R^2$  value presented in Table 2, it could be observed that Langmuir isotherm was best fitted for the adsorption of Ni(II) onto ES and CES compared with other isotherms. Suitability of experimental data with Langmuir isotherm indicated that the adsorbent ES and CES were homogenous, equal adsorption energy for each Ni(II) and ES/CES adsorption, as well as monolayer formation at the outer surface of the adsorbent. From the value of  $K_f$  and also  $q_m$ , it could be observed that calcination had given significant increase to the adsorption capacity. We speculate that this increase was possible due to more porous structure that formed during calcination process, thus increasing its surface area [27]. It is known that adsorbent performance is highly dependent to its surface area.

## CONCLUSION

In this paper, the effect of eggshell calcination to its performance as Ni(II) adsorbent was presented. The

calcination had significantly increased the adsorption capacity to 60 times, observed in Langmuir and Dubinin-Radushkevich isotherm, compared with the uncalcined one. It was also observed that the adsorption process was physisorption and exothermic. Langmuir isotherm was well fitted to the experimental data, indicating monolayer adsorption onto the homogenous surface of adsorbents. This finding indicates that simple calcination process of eggshell waste could significantly increase its performance as Ni(II) adsorbent.

## ACKNOWLEDGMENTS

This study is funded by Parahyangan Catholic University Research and Community Service Institute under contract number III/LPPM/2017-01/37-P. The authors are immensely grateful for the financial support.

## REFERENCES

- [1] Nagajyoti, P.C., Lee, K.D., and Sreekanth, T.V.M., 2010, Heavy metals, occurrence and toxicity for plants: A review, *Environ. Chem. Lett.*, 8 (3), 199–216.
- [2] Hunt, J.W., Anderson, B.S., Phillips, B.M., Tjeerdema, R.S., Puckett, H.M., Stephenson, M., Tucker, D.W., and Watson, D., 2002, Acute and chronic toxicity of nickel to marine organisms: Implications for water quality criteria, *Environ. Toxicol. Chem.*, 21 (11), 2423–2430.
- [3] Das, K.K., Das, S.N., and Dhundasi, S.A., 2008, Nickel, its adverse health effects & oxidative stress, *Indian J. Med. Res.*, 128 (4), 412–425.

- [4] The Ministry of Environment, 2014, *Peraturan Menteri Lingkungan Hidup Republik Indonesia Nomor 5 Tahun 2014 Tentang Baku Mutu Air Limbah*, Jakarta.
- [5] Fu, F., and Wang, Q., 2011, Removal of heavy metal ions from wastewaters: A review, *J. Environ. Manage.*, 92 (3), 407–418.
- [6] Oliveira, D.A., Benelli, P., and Amante, E.R., 2013, A literature review on adding value to solid residues: Egg shells, *J. Cleaner Prod.*, 46, 42–47.
- [7] Ministry of Agriculture Republic Indonesia, 2016, *Produksi Telur Ayam Ras Petelur Menurut Provinsi*, [http://www.pertanian.go.id/ap\\_pages/mod/datanak](http://www.pertanian.go.id/ap_pages/mod/datanak), accessed on 4 October 2016.
- [8] Schaafsma, A., van Doormaal, J.J., Muskiet, F.A.J., Hofstede, G.J.H., Pakan, I., and van der Veer, E., 2002, Positive effects of a chicken eggshell powder-enriched vitamin-mineral supplement on femoral neck bone mineral density in healthy late postmenopausal Dutch women, *Br. J. Nutr.*, 87 (3), 267–275.
- [9] Wei, Z., Xu, C., and Li, B., 2009, Application of waste eggshell as low-cost solid catalyst for biodiesel production, *Bioresour. Technol.*, 100 (11), 2883–2885.
- [10] Liao, D., Zheng, W., Li, X., Yang, Q., Yue, X., Guo, L., and Zeng, G., 2010, Removal of lead(II) from aqueous solutions using carbonate hydroxyapatite extracted from eggshell waste, *J. Hazard. Mater.*, 177 (1-3), 126–130.
- [11] Park, H.J., Jeong, S.W., Yang, J.K., Kim, B.G., and Lee, S.M., 2007, Removal of heavy metals using waste eggshell, *J. Environ. Sci.*, 19 (12), 1436–1441.
- [12] Flores-Cano, J.V., Leyva-Ramos, R., Mendoza-Barron, J., Guerrero-Coronado, R.M., Aragón-Piña, A., and Labrada-Delgado, G.J., 2013, Sorption mechanism of Cd(II) from water solution onto chicken eggshell, *Appl. Surf. Sci.*, 276, 682–690.
- [13] Kuh, S.E., and Kim, D.S., 2000, Removal characteristics of cadmium ion by waste egg shell, *Environ. Technol.*, 21 (8), 883–890.
- [14] Chojnacka, K., 2005, Biosorption of Cr(III) ions by eggshells, *J. Hazard. Mater.*, 121 (1-3), 167–173.
- [15] Daraei, H., Mittal, A., Noorisepehr, M., and Mittal, J., 2015, Separation of chromium from water samples using eggshell powder as a low-cost sorbent: kinetic and thermodynamic studies, *Desalin. Water Treat.*, 53 (1), 214–220.
- [16] Yeddou, N., and Bensmaili, A., 2007, Equilibrium and kinetic modeling of iron adsorption by eggshells in a batch system: effect of temperature, *Desalination*, 206 (1-3), 127–134.
- [17] Pettinato, M., Chakraborty, S., Arafat, H.A., and Calabro, V., 2015, Eggshell: A green adsorbent for heavy metal removal in an MBR system, *Ecotoxicol. Environ. Saf.*, 121, 57–62.
- [18] Vijayaraghavan, K., Jegan, J., Palanivelu, K., and Velan, M., 2005, Removal and recovery of copper from aqueous solution by eggshell in a packed column, *Miner. Eng.*, 18 (5), 545–547.
- [19] Polat, A., and Aslan, S., 2014, Kinetic and isotherm study of copper adsorption from aqueous solution using waste eggshell, *J. Environ. Eng. Landscape Manage.*, 22 (2), 132–140.
- [20] Otun, J.A., Oke, I.A., Olarinoye, N.O., Adie, D.B., and Okuofu, C.A., 2006, Adsorption isotherms of Pb(II), Ni(II) and Cd(II) ions onto PES, *J. Appl. Sci.*, 6 (11), 2368–2376.
- [21] Aslan, S., Polat, A., and Topcu, U.S., 2015, Assessment of the adsorption kinetics, equilibrium and thermodynamics for the potential removal of Ni<sup>2+</sup> from aqueous solution using waste eggshell, *J. Environ. Eng. Landscape Manage.*, 23 (3), 221–229.
- [22] Ince, M., 2014, Comparison of low-cost and eco-friendly adsorbent for adsorption of Ni(II), *At. Spectrosc.*, 35 (5), 223–233.
- [23] Haar, K.T., and Westerveld, W., 1948, The colorimetric determination of nickel as Ni<sub>4</sub> dimethylglyoxime, *Recl. Trav. Chim. Pays-Bas*, 67 (1), 71–81.
- [24] Pornchai, T., Putkham, A.I., and Putkham, A., 2016, Effect of calcination time on physical and chemical properties of CaO- catalyst derived from industrial-eggshell wastes, *J. Sci. Technol. MSU*, 35 (6), 693–697.

- [25] Kösea, T.E., and Kivanç, B., 2011, Adsorption of phosphate from aqueous solutions using calcined waste eggshell, *Chem. Eng. J.*, 178, 34–39.
- [26] Marques Correia, L., Cecilia, J.A., Rodríguez-Castellón, E., Cavalcante, C.L.Jr., and Vieira, R.S., 2017, Relevance of the Physicochemical Properties of Calcined Quail Eggshell (CaO) as a Catalyst for Biodiesel Production, *J. Chem.*, 2017, 5679512.
- [27] Witoon, T., 2011, Characterization of calcium oxide derived from waste eggshell and its application as CO<sub>2</sub> sorbent, *Ceram. Int.*, 37 (8), 3291–3298.
- [28] Galván-Ruiz, M., Hernández, J., Baños, L., Noriega-Montes, J., and Rodríguez-García, M.E., 2009, Characterization of calcium carbonate, calcium oxide, and calcium hydroxide as starting point to the improvement of lime for their use in construction, *J. Mater. Civ. Eng.*, 21 (11), 694–698.
- [29] Tan, Y.H., Abdullah, M.O., Nolasco-Hipolito, C., and Taufiq-Yap, Y.H., 2015, Waste ostrich- and chicken-eggshells as heterogeneous base catalyst for biodiesel production from used cooking oil: Catalyst characterization and biodiesel yield performance, *Appl. Energy*, 160, 58–70.
- [30] Tangboriboon, N., Kunanuruksapong, R., and Sirivat, A., 2012, Preparation and properties of calcium oxide from eggshells via calcination, *Mater. Sci.*, 30 (4), 313–322.
- [31] Mohadi, R., Anggraini, K., Riyanti, F., and Lesbani, A., 2016, Preparation calcium oxide (CaO) from chicken eggshells, *SJE*, 1 (2), 32–35.
- [32] Guru, P.S., and Dash, S., 2014, Sorption on eggshell waste—A review on ultrastructure, biomineralization and other applications, *Adv. Colloid Interface Sci.*, 209, 49–67.
- [33] Zhang, X., and Wang, X., 2015, Adsorption and Desorption of nickel(II) ions from aqueous solution by a lignocellulose/montmorillonite nanocomposite, *PLoS One*, 10 (2), e0117077.
- [34] Hannachi, Y., Shapovalov, N.A., and Hannachi, A., 2010, Adsorption of Nickel from aqueous solution by the use of low-cost adsorbents, *Korean J. Chem. Eng.*, 27 (1), 152–158.
- [35] Limousin, G., Gaudet, J.P., Charlet, L., Szenknect, S., Barthès, V., and Krimissa, M., 2007, Sorption isotherms: A review on physical bases, modeling and measurement, *Appl. Geochem.*, 22 (2), 249–275.
- [36] Foo, K.Y., and Hameed, B.H., 2010, Insights into the modeling of adsorption isotherm systems, *Chem. Eng. J.*, 156 (1), 2–10.
- [37] Ayawei, N., Ebelegi, A.N., and Wankasi, D., 2017, Modelling and interpretation of adsorption isotherms, *J. Chem.*, 2017, 3039817.
- [38] Hameed, B.H., and Ahmad, A.A., 2009, Batch adsorption of methylene blue from aqueous solution by garlic peel, an agricultural waste biomass, *J. Hazard. Mater.*, 164 (2-3), 870–875.
- [39] Hamdaoui, O., and Naffrechoux, E., 2007, Modeling of adsorption isotherms of phenol and chlorophenols onto granular activated carbon Part I. Two-parameter models and equations allowing determination of thermodynamic parameters, *J. Hazard. Mater.*, 147 (1-2), 381–394.
- [40] Sampranpiboon, P., Charnkeitkong, P., and Feng, X., 2014, Equilibrium isotherm models for adsorption of zinc(II) ion from aqueous solution on pulp waste, *WSEAS Trans. Environ. Dev.*, 10, 35–47.
- [41] Hsieh, C.T., and Teng, H., 2000, Langmuir and Dubinin–Radushkevich analyses on equilibrium adsorption of activated carbon fabrics in aqueous solutions, *J. Chem. Technol. Biotechnol.*, 75 (11), 1066–1072.
- [42] Kumar, P.S., Ramalingam, S., Kirupha, S.D., Murugesan, A., Vidhyadevi, T., and Sivanesan, S., 2011, Adsorption behavior of nickel(II) onto cashew nutshell: Equilibrium, thermodynamics, kinetics, mechanism and process design, *Chem. Eng. J.*, 167 (1), 122–131.